

Synthesis and Characterization of Carboxymethyl *Plectranthus esculentus* Starch. A Potential Disintegrant

O. Adeyanju^{1,*}, O. P. Olademihin¹, Y. Hussaini², U. C. Nwanta¹, A. I. Adejoh¹ And J. Plavec³

¹Department of Chemistry, University of Jos, Jos, Nigeria.

²Department of Science Laboratory Technology, Federal College of Forestry, Jos, Nigeria.

³National Institute of Chemistry, NMR Centre, Ljubljana, Slovenia.

Received: 5 Feb. 2016, Revised: 12 May 2016, Accepted: 15 May 2016.

Published online: 1 Sep. 2016.

Abstract: *P. esculentus* starch was chemically modified via carboxymethylation. The product was characterized using Scanning electron Microscopy (SEM), Fourier Transform Infrared (FTIR) and Nuclear Magnetic Resonance (NMR) spectroscopy. Physicochemical characteristics of the native and carboxymethyl starch such as Viscosity, solubility, Swelling power and viscosity-average molecular weight were also determined. The result showed that the starch from *P. esculentus* starch is composed of α -glucose linked together at 1 \rightarrow 4. The carboxymethyl starch with degree of substitution 0.40 ± 0.02 had higher physicochemical properties than the native starch. The result showed that chemical modification by carboxymethylation may improve the physicochemical properties of polysaccharides resulting in higher efficacy for effective utilization in starch-based industries.



Keywords: Carboxymethylation, *Plectranthus esculentus*, starch, excipient

1 Introduction


Starch is a natural, cheap, available, renewable and biodegradable polymer produced by many plants as a source of stored energy [1]. It has found wide use in the food, textiles, cosmetics, plastics, adhesives, paper and most importantly pharmaceutical industries [4]. In the year 2000, the world starch market was estimated to be 48.5 million tons, including native and modified starches. The value of the output is worth €15 billion per year [3]. Worldwide, the main sources of starch are Maize (82%), wheat (8%), potatoes (5%) and cassava (5%). [3].

Modified starches have played a major role in the food and pharmaceutical industries over the past few decades. They possess unique properties not found in natural starches, which are suitable for the development of new products [2]. The chemical modification of polysaccharide is the most important route to modify the properties of the naturally occurring biopolymers and to use this renewable resources in the context of sustainable development [5-6]. Carboxymethyl starch is a popular chemically modified starch. It is prepared by the reaction of starch (St-OH) and monochloroacetic acid in the presence of sodium hydroxide [7-9]. This is a two-step reaction, according to the Williamson ether synthesis yielding the carboxymethyl

polysaccharide derivative [9].



An undesired reaction of sodium monochloroacetic acid with NaOH can also occur



The amount of substituted carboxymethyl group is indicated by the degree of substitution (DS). The DS is defined as the average number of substituents per glucose unit. Each glucose unit contains three hydroxyl groups (C₂, C₃ and C₆); therefore, the DS lies between zero and three. From the studies of Volkert *et al.* [9] and Heinze *et al.*, [10], substitution in the order C₂>C₆>C₃ was indicated. The plant *Plectranthus* belong to the mint family *Lamiaceae* to which many aromatic plants belong. It is a perennial herb, which is sparsely branched and grows up to 2m in height [11]. Despite this fact, this species is a kind of potato [12]. The tubers are cultivated for food in Africa, particularly in the Northern parts of Nigeria around Adamawa, Bauchi, Niger, Kaduna and most importantly Jos, Plateau State [13]. The tubers are rich in Vitamin A and Iron. The leaves are used in the treatment of various ailments such as respiratory and digestive problems [14]. Other modification types and their utilization as excipients in drug formulation have been

* Corresponding author E-mail: adeyanju.olusola@yahoo.com

reported[36]. Nutrient content of *P. esculentus* starch and tuber has also been reported [36]. Therefore, this study was designed to modify the starch from *P. esculentus* by carboxymethylation and evaluate the effect of carboxymethylation on some physicochemical properties of the native starch. The result of this research may likely highlights the effect of carboxymethylation on the physicochemical properties of *P. esculentus* starch for possible application as excipient in drug formulation.

2 Materials and Methods

2.1 Extraction of *P. esculentus* Starch

P. esculentus potatoes tubers were obtained from Angwarukuba market, Jos, Nigeria, washed, peeled, and trimmed to remove defective parts. The tubers were then sliced, diced, and blended with distilled water in a food blender. The mixture was sieved through an 80-mesh screen, and the retained solid was exhaustively rinsed on the sieve with distilled water. The filtrate was allowed to stand overnight at 15°C, the precipitate was collected, and the supernatant was discarded. Resuspension and sedimentation operations were repeated until white starch was obtained. The starch was dried at 50°C for 6hrs. finally, the dried potatoe flir was ground and passed through a 100-mesh sieve. Potatoe starch was kept in a tight light-resistant container.

2.2 Preparation of Carboxymethyl *P. esculentus* Starch

In the standard preparation, the native potatoe starch (10.0g) was suspended in 2-propanol (100mL). An aqueous sodium hydroxide solution was added (3% W/v (10ml)). The mixture was stirred at controlled temperature (30°C) for 10min. Sodium monochloroacetate was added and stirring was continued up to the designated time. The pH of the mixture was adjusted to about 5.0 by addition of 50% glacial acetic acid. The carboxymethyl starch was filtered and washed with aqueous ethanol. The modified starch was dried at 50°C for 6hrs, the dried carboxymethyl starch was passed through a 100-mesh sieve.

2.3 Determination of the Degree of Substitution (DS)

The DS of carboxymethyl starch (CMS) was determined in accordance with the method reported by Stojanovic *et al.*, [15]. The carboxymethyl groups in the CMS were first converted to an acid form with hydrochloric acid (HCl). The acidified starch was then recovered by precipitation with methanol, Filtration, washing with methanol and drying. Then, 0.2 M NaOH (10ml) was added to a suspension of accurately 1g weighed CMS in 10 mL of purified water. The mixture was transferred to a 100-mL

volumetric flask and adjusted to the mark with purified water. The solution (25 mL) was transferred to an Erlenmeyer flask and titrated with 0.04M HCl using phenolphthalein as the indicator. The titration was repeated three times, and the average value of HCl volume was used for the calculations. A blank was also titrated. The DS was calculated using followed equations:

$$DS = \frac{162 \times nCOOH}{m_{ds} - 58 \times nCOOH} \text{---(4)}$$

$$m_{ds} = \frac{(1 - W_{water})}{100} \times ms \text{---(5)}$$

$$nCOOH = (V - V_n) \times C_{HCl} \times 4 \text{---(6)}$$

Where 162 is the molar mass of anhydrous glucose unit (in g/mol); $nCOOH$ (in mol) is the amount of COOH; m_{ds} (in g) is the mass of dry sample; ms (in g) is sample mass; W_{water} (%) is water content; V_0 (in mL) is the volume of HCl used for the titration of the blank; V_n (in mL) is the volume of HCl used for the titration of the sample; C_{HCl} (in mol/L) is the HCl concentration; and 4 is the ratio of the total solution volume (100mL) and the volume taken for titration (25 mL).

2.4 Determination of Physicochemical Properties of Starch

2.4.1 Viscosity

The viscosity of a 2% w/v starch suspension was determined using a viscometer (Brookfield, RVDV-II+PRO, USA) with a spindle no. RV-02 and a speed of 200 rpm of 200 at 25°C. the readings of viscosity were taken after 30s of rotation. All measurements were performed in triplicate.

2.4.2 Swelling Power

The swelling power (by weight) of starch was measured using a method modified from the one reported by Tester and Marison [16]. Potatoe starch (0.2g) was dispersed in water (20 mL). The suspension was heated to 85°C in a water bath for 30min with vigorous shaking every 5min. the starch gel was then centrifuged at 2,200 rpm for 15 min. the weight of sediment was used to calculate the swelling power, and expressed in percent. The determination was done in triplicate. The swelling power was calculated as follow:

$$\text{Swelling power} = \frac{\text{Weight of sediment}}{(\text{Weight of dry starch} - \text{Weight of dissolve starch})} \text{---(7)}$$

2.4.3 Solubility

The solubility of starch was determined. Starch sample 10g was suspended in 40ml of distilled water. It was heated to the desired temperature 60°C, 70°C or 80°C for 30 minutes

with continuous shaking. The mixtures were centrifuged at 100rpm for 15 minutes. An aliquot of supernatants (5ml) were evaporated at 130°C and weighed. The solubility's of the starch were the percentage ratio in mass(g) of the dried supernatant to the initial mass (g) of the dry starch.

2.4.4 Weight-average Molecular Weight (M_w)

Native and modified starch samples with a range of molecular distributions were analysed by dilution solution viscosity. Based on the M_w (weight average molecular weight) and intrinsic viscosity $[\eta]$ values of a standard starch solutions, a plot of $\log [\eta]$ against $\log M_w$ yielded a straight line. From the plot, K and a values were determined (slope and intercept). The molecular weight of the starch was determined by Mark-Houwink equation, $[\eta]=KM_w^a$, where M_w is the viscosity-average molecular weight and the parameters K and a are related to local stiffness of the polymer and depend on the nature of the polymer, solvent and temperature. The molecular weight (M_w) of the polysaccharide was measured using viscometer and the molecular weight obtained by this technique called viscosity-average molecular weight.

2.4.5 Microstructure studies by SEM;

Morphological features of the native starch and the carboxymethylated starch was studied with a JSM-5600LV scanning electron microscope of JOEL (Tokyo, Japan). The dried sample was mounted on a metal stub and sputtered with gold in order to make the sample conductive, and the images were taken at an accelerating voltage of 10KV and at 500x magnification.

2.4.6 Fourier Transform Infrared (FTIR) and Nuclear Magnetic Resonance (NMR)

The FTIR spectrum of the starch samples were recorded in an FTIR spectrometer (Nicolet Magna 4R 560. MN USA) using potassium bromide (KBr) discs prepared from powdered samples mixed with dry KBr. Solid State NMR of *p. esculentus* starch and carboxymethylated starch were recorded in an NMR (600 MHz) spectrometer (Agilent technologies, America).

3 Results and Discussion

$$V_o = \frac{(25+25)}{2} = 25cm^3$$

$$V_n = \frac{(21.3 + 21.45)}{2} = 21.375cm^3$$

$$M = \frac{(0.5013 + 0.5035)}{2} = 0.5024g$$

$$M = 0.3moldm^{-3}$$

$$\text{carboxymethyl content (\%)} = \frac{[(V_o - V_n)M \times 0.059 \times 100]}{m}$$

$$= \frac{[(25 - 21.375)0.3 \times 0.059 \times 100]}{0.5024} = 12.7712\%$$

$$DS = \frac{162 \times \%CM}{[5900 - (58 \times \%CM)]}$$

$$= \frac{162 \times 12.7712}{[5900 - (58 \times 12.7712)]} = 0.4010$$



Fig 1: *P. esculentus* tubers.

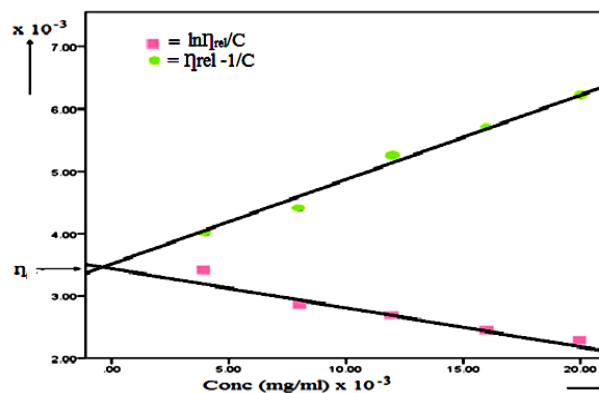


Fig 2: Intrinsic viscosity of native *P. esculentus* starch

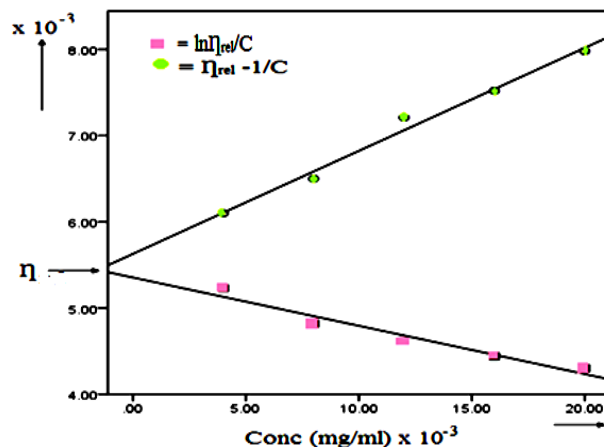


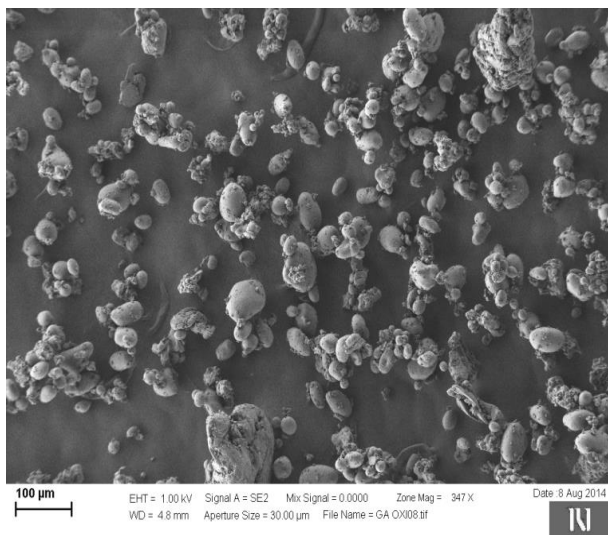
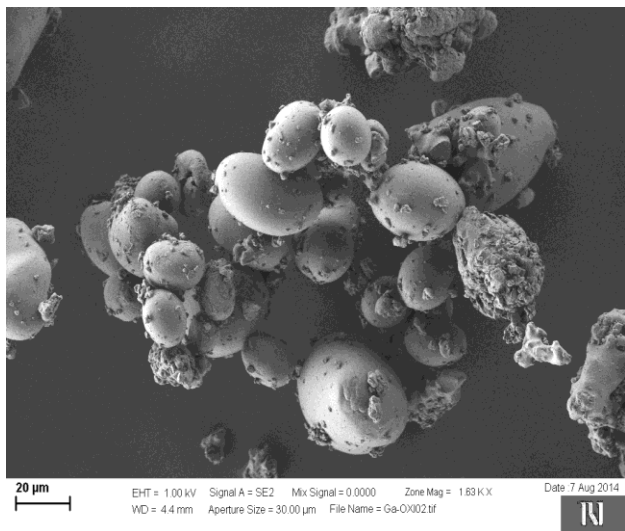
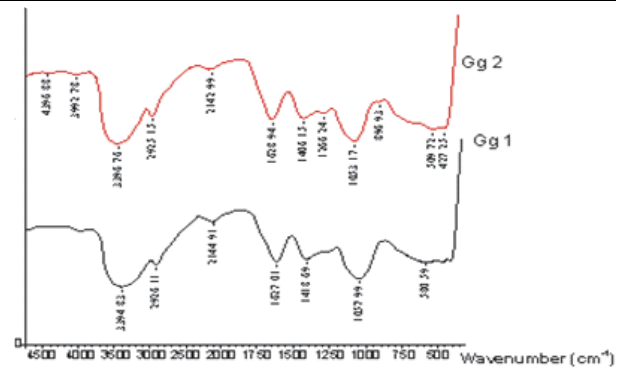
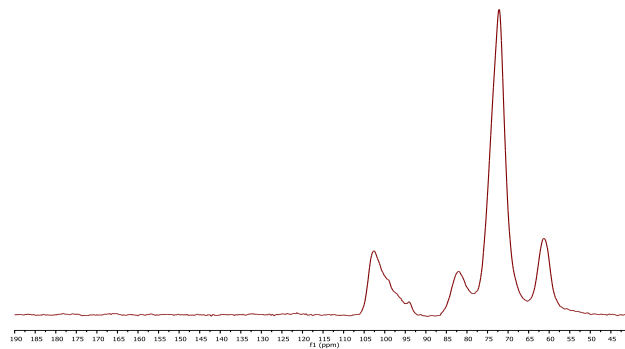
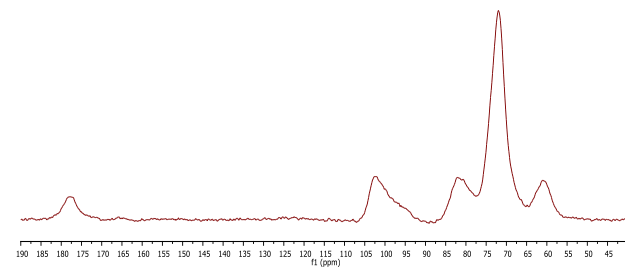
Fig 3: Intrinsic viscosity of Carboxymethyl *P. esculentus* starch.

Table 1: Physicochemical characteristics of the native and carboxymethyl *P. esculentus* starch

Type	Solubility (%)		Swelling power (%)	Viscosity (M.Pa.S)	Molecular weight (g/mol)
Native starch	60°C	1.20±0.01	7.54±0.13	24.64±0.90	6.02 ×10 ⁵
	70°C	10.50±0.2			
	80°C	15.40±0.1			
Carboxymethyl starch	60°C	3.8.4±1.5	19.90±0.25	40.90±0.20	10.4×10 ⁵
	70°C	54.5±2.7			
	80°C	89.7±1.6			

Table 2: Titration Result for the determination of the carboxymethyl content and Degree of Substitution

%	Blank			Sample				
NaOH-CMS (%)	Weight M ₀ (g)	V _i (cm ³)	V _i (cm ³)	V ₀ (cm ³)	Weight M ₀ (g)	V _i (cm ³)	V _t (cm ³)	V _n (cm ³)
10%	0.5006	0.05	25.05	25.00	0.5013	0.30	21.60	21.30
	0.5003	0.00	25.00	25.00	0.5035	0.25	21.70	21.45

**Fig 4:** SEM Image of native *P. esculentus* Starch**Fig 5:** SEM Image of carboxymethyl *P. esculentus* starch**Fig 6:** FTIR of native (Gg1) and carboxymethyl (Gg2) *P. esculentus* starch**Fig 7:** Solid state ¹³C- NMR of Native *P. esculentus* starch**Fig 8:** Solid state ¹³C- NMR of carboxymethyl *P. esculentus* starch.

4 Discussion of Results

The viscosity, swelling power and solubility compared favourably with other commercial starches previously studied by other authors [17, 18]. Swelling is a primary mechanism in diffusion controlled release dosage form [19]. The viscosity, swelling power, solubility and molecular weight for carboxymethyl starch 40.90 ± 0.20 MPa.S, $17.90 \pm 0.25\%$, $89.7 \pm 1.6\%$ (at 80°C) and 10.4×10^5 g/mol were higher than the native starch 24.64 ± 0.90 MPa.S, $7.54 \pm 0.13\%$, $15.40 \pm 0.1\%$ (at 80°C) and 6.02×10^5 g/mol. (Table 1).

The result shows that the carboxymethyl starch when used as a binder/disintegrant could absorb sufficient moisture to swell and cause tablets to disintegrate and burst and free up sufficient energy to release drug content. [20]. Carboxymethylation generally increases the viscosity and water holding capacity [10]. During carboxymethylation process, the gum-gum interaction in the granules are weakened by the introduction of carboxymethyl groups, this makes the starch to be more attracted towards water molecules [5-8].

Henry[23] reported that introduction of carboxymethyl group reduces the bond strength between starch molecules (amylase/amylopectin) and thereby increases the swelling power and solubility of the starch granules. This facilitates access of water to amorphous areas, enhancing the viscosity [20]. The superior solubility and swelling power of the carboxymethyl starch compared with the native starch may be due to the presence of hydrophilic substituting groups ($\text{CH}_2\text{C}=\text{O}$) which allow the retention of water molecules because of their ability to form hydrogen bonds [20]. The increase in the viscosity of the carboxymethyl starch may also be due to the steric hinderance exhibited by the bulky carboxymethyl groups which obstruct the proper alignment of starch chain for maximum retrogradation [20].

Adding bulky functional groups like carboxyethyl and carboxymethyl groups reduces the tendency of the starch to recrystallize and make the starch less prone to damage by heat and bacteria [20]. NaOH increases the reactivity of starch towards chemical reaction as compared to the untreated starch. Thus, it means that etherifying or esterifying reagents are able to penetrate the swelled starch structure more easily and thus substitution of the hydroxyl group of the anhydrous glucose unit becomes easier [8-10].

Molecular weight and concentration are two most important characteristic of polymers synthesized through chemical or microbial processes [21]. However, current methods for characterizing polymer molecular weight such as Multi-Angle Laser Light Scattering (MALLS) or Gel-Angle Laser Light Scattering (GPC) require long processing and analysis, expensive equipment, high sample concentration and high sample volume [21]. Therefore in this study, viscometry method was used to determine the molecular

weight of the polysaccharides. This is because of its low cost and is able to evaluate the differences in polymer viscosity for varying molecular weight and solvent conditions.

The experimentally determined relative viscosity (η_{rel}) were used to plot $\eta_{rel}-1/c$ vs concentration and to determine the intrinsic viscosity by extrapolating to concentration $C=0$, if $\eta = \eta_o$, it can be shown that $(\eta/\eta_o)-1$. $[\eta]$ may be determined from the limiting behavior of $(1/C)$ and 1η (η/η_o) as $C \rightarrow 0$. Plotting both functions enables the intrinsic viscosity to be obtained with greater precision. K and a which are constants were derived by charting out a series of $[\eta]$ values Vs the known molecular weight in a log-log plot. This relationship is derived from Mark-Houwink equation $[\eta]=KM^a$ and $\log[\eta]=\log(k) + a(\log M)$.

The viscosity-average molecular weight of starch and its derivative is shown in Table 1 and figure 2 and 3. There is a significant increase in the molecular weight of the native starch after carboxymethylation.

The Mark-Houwink relationship $[\eta]=KM^a$ was evaluated as $K=2.0 \times 10^4$ and $a=0.75$ for a standard starch in 0.1M aqueous NaCl at 25°C , the low value of the exponent a is characteristic of a branched polymer [22]. The viscosity average-molecular weight of native and carboxymethylated starch (Table 1) were found to be 6.02×10^5 g/mol and 10.40×10^5 g/mol respectively. The increase in the molecular weight could be due to the presence of bulkier carboxymethyl groups in the native starch [22].

The degree of substitution (DS) was determined not based on the total monosaccharide unit but on free Unit. The degree of substitution (Table 2) was determined as 0.4010 ± 0.02 . modified polysaccharide with low DS (< 0.1) are used in the food industries since they confer consistency, texture and stability while polysaccharide with high DS (> 0.1) are used in the pharmaceuticals [24]. Different values of DS were obtained for other carboxymethyl starches in other studies [7, 25, 26].

SEM

The SEM images of *P. esculentus* starch and the carboxymethyl starch are represented in fig 4-5. The starch granules are observed to be predominantly elliptical with a smooth surface while the granules of the carboxymethyl starch are markedly different from the native. The granules of the carboxymethyl have indented surfaces and some areas on the granules surface become shrunken and even broken. Alkaline treatment may be responsible for the changes, it is possible that the changes observed on the starch granules are due to the loss of crystalline structure affected by alkaline conditions. This means that the carboxymethylation reaction occurs on the surface of starch granules as well as the inside. The granule morphology of the carboxymethyl starch prepared by this method has

similar appearance as those found in other studies [27, 28, 29].

FTIR spectroscopy

The infrared spectra of the native and carboxymethyl starch with DS 0.4 is shown in fig 6. The broad band between 3600 and 3000 cm^{-1} is assigned to O-H stretching and it is due to hydrogen bonding involving the hydroxyl groups in the starch molecules. The band at around 2922 cm^{-1} is assigned to CH_2 symmetrical stretching vibrations and the band around 1600 and 1420 cm^{-1} , there is strong absorption peaks for asymmetric and symmetric vibration of COO^- in the spectrum of the carboxymethyl starch. This bond confirms the introduction of $-\text{OCH}_2\text{COO}^-$ group into the starch molecule [30].

Solid state ^{13}C -NMR

The NMR spectra of the native and carboxymethyl starch is shown in fig 7-8. The spectra gave line widths which are typical of an amorphous natural polysaccharide with broad band signal between 64 and 90 ppm arising from the bulk of the ring, C-OH. The C-4 carbon accounts for the high frequency shoulder while C-1 anomeric carbon gave the signal between 90 and 110 ppm. The shape of this band suggests it is composed of multiple signals but the low resolution suggests the contrary. The low intensity at about 62 ppm is attributable to the $-\text{CH}_2\text{OH}$ belonging to glucose [30-35]. The resonance of the carbon atoms were resolved (fig 7) and identified as the resonances of C-1 (102.66), C-2 (94.07), C-3 (81.83), C-4 (72.32), C-5 (61.29) and C-6 (61.4) of α -glucose. The ^{13}C -Solid state NMR for the carboxymethylated starch showed signals at 176.5 ppm assigned to the carbonyl carbon of carboxymethyl groups (fig 8). The carboxymethylated starch ^{13}C -Solid state NMR spectra (fig 8) showed a decrease in signal intensities at both the C-6 and C-4 peaks indicating that the polysaccharide underwent a preferred degradation of the crystalline region during carboxymethylation [32, 34].

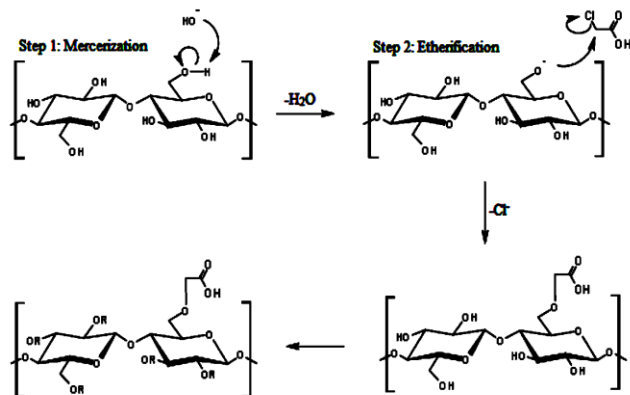


Fig. 9: Mechanism for Carboxymethylation of Starch

5 Conclusion

Carboxymethylated *P. esculentus* starch was synthesized and characterized. The new carboxymethyl group was detected by FTIR and NMR analysis. The carboxymethylation occurs preferentially at the primary carbons of glucose units as observed by NMR analysis. A high viscosity, swelling power, solubility and molecular weight were observed for aqueous solutions of carboxymethyl starch in comparison to the unmodified starch. The study confirms that carboxymethylation improves the properties of the native starch. It is more attractive because the starch from *P. esculentus* is a natural, abundant, non-toxic, low cost and regional raw material. This material may be utilized as binder or disintegrant in solid dosage formulation.

Acknowledgement

The authors are grateful to Sheda Science Complex (SHETSCO) Abuja, Nigeria, National Research Institute Zaria, Nigeria and National Institute of Chemistry, NMR Centre, Ljubljana, Slovenia for their Technical Support.

References

- [1] Kittipongpatana, O.S., Sirithunyalung, J. and Leanger, R. (2006). Preparation and physicochemical properties of sodium carboxymethylmungbean starches. *Carbohydrate polymer*. 63: 105-112.
- [2] Stojanovic, Z.J. and Jovanovic, S. (2000). Synthesis of carboxymethyl Starch. *Starch*. 52:413-419.
- [3] Le Corre, D., Bras, J. and Dufresne, A. (2010). Starch Nanoparticles: A Review. *Biomacromolecules*. 11(5): 1139-1153.
- [4] Emeje, M.O. and Asha, R. (2012). Starch: from food to medicine, scientific, Health and Social Aspects of the food Industry. Dr. Benjamin Valdez (Ed). 200-206.
- [5] Jarowrenko, W. (1986). "Pregelatinised starches". In O.B. Wurzburg (Ed). Modified starches, properties and Uses Boca Raton, FL. CRC Press: 71.
- [6] Lewandowicz, G. and Soral-Smietana, M. (2004). Starch modification by iterated syneresis. *Carbohydrate polymer*. 56(4): 403-413.
- [7] Tijssen, C.J., Kolk, H.J., Stamhuis, E.J. and Beenackers, A.A. (2001). An experimental study on the carboxymethylation of granular potato starch in non-aqueous media. *Carbohydrate polymer*. 45:219-226.
- [8] Kooijman, L.M., Ganzeveld, K.J., Manurung, R.M. and J Heeres, H. (2003). Experimental studies on the carboxymethylation of arrow root starch in isopropanol-water media. *Starch*. 55: 495-503.
- [9] Volkert, B., Loth, F., Lazik, W. and Englehardt, J. (2004). Highly substituted carboxymethyl starch. *Starch*. 56: 307-314.

- [10] Heinze, T., Pfeiffer, K., Liebert, T. and Heinze, U. (1999). Effective approaches for estimating the functionalization pattern of carboxymethyl starch of different origin starches. *Starch*. 51(1): 11-16.
- [11] Allemann, J. and Hammes, P.S. (2003). Chemical composition of South Africa *Plectranthus esculentus* tubers. *South African Journal of science*. 99: 127-129.
- [12] Gila, M.A. (1984). Morphogenetic variation in 'Rizga'. *Plectrathus esculentus* N.E.Br. M.Sc thesis, Department of Botany, University of Jos, Jos, Nigeria. 1-3.
- [13] Kyemusu, P.M. (1994). Fats and Oils: An outline of their Chemistry and Technology. Reinhold Publishing Corporation, New York.
- [14] Schippers, R.R. (2000). African indigenous vegetables. An overview of the cultivated species. Natural resources Institute/ACP-EU Technical Centre for Agricultural and Rural Cooperation, Chatham, United Kingdom. Pp 214.
- [15] Stojanovic, Z., Jeremic, K., Jovanovic, S. and Lechnew, D.M. (2005). A comparison of some methods for determination the degree of substitution of carboxymethyl starch. *Starch*. 51: 79-83.
- [16] Tester, R.F. and Marison, W.R. (1990). Swelling and gelatinization of cereal starch. Effect of Amylopectin, amylase and lipids. *Cereal Chem*. 67: 551-557.
- [17] Kittipongpatana, O.S., Chaitap, W., Laenger, R. and Siroth, K. (2007). Physicochemical and Pharmaceutical properties of carboxymethyl Rice starches. *Cereal chemistry*. 84(4): 331-336
- [18] Lia, I.H., Ramsden, L. and Corke, H. (1999). Physicochemical properties of modified and normal maize starch. *Carbohydrate Polymer*. 40 (3): 175-182.
- [19] Achayuthakan, P. and Suphantharika, M. (2008). Pasting and Rheological properties of waxy corn starch as affected by guar gum and xanthan gum. *Carbohydrate polymers*. 71:9-12.
- [20] Heinze, T. (2005). Carboxymethyl Ethers of cellulose and starch; A review. *Chemistry of plant raw material*. 3: 13-29.
- [21] Hakeem, (2008). Physicochemical properties of cashew tree gum. *African Journal of food science*. 2: 060-064.
- [22] De Paula, R.C.M., Sanatana, S.A. and Rodriguense, S.F. (2001). Composition and Rheological properties of Albizia gum exudates. *Carbohydrate polymers*. 44: 123-139.
- [23] Henry, M.O. (2007). Effect of chemical modification on starch of some Legume flours. *Pakistan Journal of Nutrition*. 6(2): 167-171.
- [24] Le Cerf, D., Irinei, F. and Muller, G. (1990). Solution properties of Gum exudates from *sterculinaureus* (Karaya gum). *Carbohydrate polymer*. 13: 375-380.
- [25] Sangsechthog, K., Ketsilp, S. and Sriroth, K. (2005). The role of reaction parameters on the preparation and properties of carboxymethyl cassava starch. *Starch*. 57: 84-93.
- [26] Khalil, M.I., Hasheem, A. and Hebesish, A. (1990). Carboxymethylation of maize starch. *Starch*. 42: 60-63.
- [27] Sangsechthog, K., Ketsilp, S. and Sriroth, K. (2005). The role of reaction parameters on the preparation and properties of carboxymethyl cassava starch. *Starch*. 57: 84-93.
- [28] Zhang, X., Liu, X. and Li, W.Y. (2003). Properties of starches. *Journal of applied polymer science*. 89: 3016-3017.
- [29] Li, X., Gao, W.Y. and Liu, C.X. (2010). Carbohydrate polymers. 80: 768-769.
- [30] Cheng, H.N. and Thomas, G.N. (2012). NMR spectroscopy of food polysaccharides, *Polymer reviews*. 52: 81-114.
- [31] Liitia, T., Maunu, S.L., Hortling, B., Tamminent, T. and Varhimo, A. (2003). Cellulose crystallinity and ordering of hemicelluloses in pine and birch pulps as revealed by solid state NMR spectroscopy. *Cellulose*. 10: 307-316.
- [32] Wickolm, K., Larson, P.T. and Iversen, T. (1998). Assignment of non-crystalline forms in cellulose by CP/MAS ¹³C-NMR spectroscopy. *Carbohydrate Resource*. 312: 123-129.
- [33] Duss, J.O., Gotfredsen, C.H. and Bock, K. (2000). Carbohydrate structural determination by NMR spectroscopy. Modern methods and limitation. *Chemical review*. 100: 4589-4614.
- [34] Larson, P.T., Westermarck, U. and Iverson, T. (1995). Determination of the cellulose amorphous content by CP/MAS ¹³C-NMR spectroscopy. *Carbohydrate Resource*. 278: 339-343 .
- [35] Cheng, H.N. (2012). NMR Spectroscopy of polymers in solid state. *American Chemical society*. (ACS symposium series Number 834) 1010-1013.
- [36] Ochekepe, N.A., Ursula, C.K. and Elijah, I.N. (2013). Chemical modifications and their effects on binding/disintegrating properties of *Plectranthus esculentus* starch in Chloroquine phosphate tablets. *American Journal of Pharm Tec research*. 3(3): 867-877.